

# REDUCING THE USE OF CEMENT WITH MARBLE WASTE FOR

*by 00 2*

---

**Submission date:** 19-Jun-2024 02:28PM (UTC+0700)

**Submission ID:** 2405213665

**File name:** 2.\_REDUCING\_THE\_USE\_OF\_CEMENT\_WITH\_MARBLE\_WASTE\_FOR.pdf (476.98K)

**Word count:** 5660

**Character count:** 28896



11

## REDUCING THE USE OF CEMENT WITH MARBLE WASTE FOR SEASIDE CONCRETE CONSTRUCTION THROUGH THE GRAPHITE CARBON PARTICLES SYSTEM

Muhammad <sup>36</sup>arif<sup>1</sup>, Andi Yusri<sup>1</sup>, Muh. Amir<sup>2</sup>, Nasrullah<sup>3</sup> and Suryaningsi Suryaningsi<sup>4</sup>

<sup>1</sup>Department of Architecture, Faculty of Engineering, Muhammadiyah Makassar University, Indonesia

<sup>2</sup>Department of Civil Engineering, Faculty of Engineering, Muhammadiyah Makassar University, Indonesia

<sup>3</sup>Department of Architecture Engineering, Faculty of Engineering, Bosowa University, Indonesia

<sup>4</sup>Faculty of Teacher Training and Education Mulawarman University, Indonesia

E-Mail: [muhsyarif00@unismuh.ac.id](mailto:muhsyarif00@unismuh.ac.id)

### ABSTRACT

This research aims to save the environment by <sup>13</sup>reducing the dredging of natural resources and air pollution in cement factories which produce a lot of CO<sub>2</sub> emissions through the use of marble industrial waste. By reducing the amount of cement by 25% and replacing it with Carbon Graphite Particle Marble Powder for concrete construction work with a design quality of K-250 or f<sub>c</sub>' 20.75 MPa by using it in buildings by the sea under the influence of sea air, the concrete quality is obtained higher than the quality design concrete is 22.76 MPa > 20.75 MPa. The compressive strength testing process was carried out based on ASTM C 39/C 39M - 05. Meanwhile, for workability, based on the slump test results, a 12 cm slump value was obtained with the testing process referring to SNI 1972: 2008 and ASTM C143/C143M-12. Refining marble waste using a grinder with a capacity of 5.5 HP equipped with a 200-micron filter. The combustion process uses a high-pressure combustion engine with combustion capabilities of up to 2000<sup>0</sup> C. Carbon particles are obtained at temperatures between 850<sup>0</sup> C and 900<sup>0</sup> C for 120 minutes. Temperature measurement using an Infrared Thermometer with a capacity of up to 1500<sup>0</sup> C.

**Keywords:** combustion, marble powder, compressive strength, water curing, dry curing.

25

Manuscript Received 23 April 2023; Revised 17 September 2023; Published 30 September 2023

### INTRODUCTION

The waste resulting from processing marble in marble factories in the form of marble clay powder/powder tends not to be utilized and in many countries, this waste is a problem for the factory and the surrounding community who live around the factory area.

Many studies have been conducted to find solutions for the utilization of marble clay waste. The same is true for cement factories which directly create air pollution as a result of the process of burning cement raw materials.

This research aims to provide innovations in the use of marble clay waste in substituting the use of cement so that it is hoped that the use of cement in infrastructure works and other works that use cement as a basic material can reduce its use which in turn will reduce air pollution from the combustion of cement raw materials.

Currently, the <sup>14</sup>waste problem is a world problem that will definitely have a negative impact on the environment. Increased development in the infrastructure sector demands an increase in the <sup>34</sup>amount of available building materials. The development of building materials needs to be addressed by using alternative building materials so that the preservation of nature and ecosystems can be maintained [1].

Marble is formed from the recrystallization of limestone (*limestone*) because its presence is always associated with limestone, although not every time there is limestone there will be marble. The main minerals of marble are calcite or dolomite and/or silified lime, so the silica content is high. The potential for limestone reserves

in Indonesia is very large, estimated at 28,678 billion tons [2].

Based on the results of the elemental test contained in marble waste, the highest CaO value is obtained, namely 98.63%, so that the positively charged Ca content can offset the negative charge on the clay [3].

Marble is a metamorphic rock resulting from the process of metamorphism of limestone, the process of metamorphism that occurs is influenced by temperature and pressure which can cause changes in the structure, texture and mineralogy of the limestone. <sup>4</sup>The main minerals that makeup marble are calcite (CaCO<sub>3</sub>), dolomite and other minerals, such as clay minerals, mica, quartz, pyrite, iron oxide and graphite. Calcite as a constituent of limestone (marble protolith) undergoes recrystallization in the metamorphic process [4].

The use of marble powder waste has been used in paving block research using marble powder as a substitute for fine aggregate (100% marble powder) resulting in a compressive strength-bearing capacity of 39.75 MPa, 34 MPa, 25 MPa, 20 MPa and 14 MPa respectively. - <sup>22</sup>pectively at a mixture ratio of 1:2, 1:4, 1:6, 1:8 and 1:10. The compressive strength of paving blocks using marble powder as a filler for fine aggregate (50% marble powder) is 38.75 MPa, 25.50 MPa, 15 MPa, 11 MPa and 10 MPa respectively at a mixture ratio of 1: 2, 1:4, 1:6, 1:8 and 1:10 [5].

Other studies have also been carried out to see how far the marble clay waste is capable of being used as an infrastructure material. For example, in testing the mechanical properties of expansive soil and soil mixed with



marble was [12] and, the compressive strength has increased. In general, the increase is 0.22 kg/cm<sup>2</sup> - 0.63 kg/cm<sup>2</sup> (an average of 31.71% for every 23% addition of marble sand), while the shear strength is 0.17 kg/cm<sup>2</sup> - 0.27 kg/cm<sup>2</sup> (average 27.05% for every 10% addition of marble sand) [6].

The greater the use of marble powder in the concrete mix, the concrete slump value increases. The use of marble waste cannot be fully used as an alternative material to replace cement, but it can increase the strength of concrete when using marble waste 5% by weight of cement [7].

Nanoparticles provide several benefits such as activation of cement hydration which can function to reduce the formation of Ca(OH)<sub>2</sub>, and increase strength gain. Moreover, many studies have focused on nano silicon oxide particles/SiO<sub>2</sub> to demonstrate its effectiveness in improving the strength-related properties of substituted cement [8].

Nanocarbon contains a number of properties as a filler in various types of binders used such as Portland cement, white cement, gypsum, or lime. A variety of destructive and non-destructive mechanical tests are performed, including compressive strength, flexural strength, Schmidt surface hardness, and ultrasound pulse analysis. The innovation obtained is that the ordinary binder with a compressive strength of 32.5 MPa is changed to a normal binder with a compressive strength of 42.5 MPa at 28 days only by adding nanocarbon and without increasing the cement content, which will also lead to an increase in the carbon footprint of the formulation. Therefore, continuous formulations are offered with significant strength advantages [9].

Several studies in an effort to increase the material's carrying capacity are by using carbon powder. The use of carbon powder has been performed by various researchers in the manufacture of carbon-based bricks as an addition to sand material. With reference to SNI 03-0349-1989 concerning concrete bricks for wall pairs. Mixing carbon substances in the manufacture of bricks with variations of 0%, 5%, 10%, and 15% by weight of the required sand, the cement mixture used: 25%: 70%: 5%. The results of the compressive strength test on a cube sample measuring 0.15 x 0.15 x 0.15m, for normal bricks is 259.783 kg/cm<sup>2</sup>. Bricks with a mixture of 5% get a yield of 352.893 kg/cm<sup>2</sup>. A mixture of activated carbon powder with 10% yielded the highest compressive strength of 393.293 kg/cm<sup>2</sup>. So with the addition of 10% carbon powder as an addition to fine aggregate (sand) is the right choice [17].

Nearly 10% of global carbon dioxide (CO<sub>2</sub>) emissions come from reducing CO<sub>2</sub> levels from the cement industry without significantly modifying the properties of concrete through the utilization of waste from other industries known as supplementary cementitious materials (SCMs), among others evaluating the properties of Cement Concrete Limestone-Calcined Clay, silica fume, fly ash, bagasse ash and acai stone ash. [11].

In other studies using marble waste as an ingredient in concrete mixtures has also been developed. According to Elli Mercy Julmile *et al.* [12] That the effect of using silica fume and marble stone fragments as substitution materials in concrete mixtures on split tensile strength, flexural strength of concrete and compressive strength. With a design concrete quality of 25 MPa. The compressive strength value of concrete for marble fragments is 50% against Silica Fume variations of 0%, 10%, 12.5% and 15%, so the best result is the use of silica fume of 10% with the highest value obtained 25,832 MPa. Marble, as a widely used building decoration material, produces a significant amount of waste marble powder (WMP) during processing. The results showed that increasing the Na<sub>2</sub>O dosage shortened the setting time of the binders, reduced the fluidity, and improved the strength. [6] Liu *et al.* [13].

The building materials industry is always a source of waste which is most often throw out in landfills or in the nature, which has negative effects on the environment. For this purpose, in Western countries, this type of rejection is strictly prohibited and the management of solid waste, whether by valorization or recycling, remains a major concern [5].

In recent years, the volume of waste marble powder (WMP) from ornamental stone factories has increased rapidly, causing environmental concerns of soil, water and air pollution. While some studies have explored the benefits of incorporating WMP in concrete mixtures, the lack of pertinent data and a comprehensive understanding of how WMP influences the engineering properties of concrete has hindered the large-scale applications of WMP in the concrete industry [15].

## METHODOLOGY

For the process of refining marble waste in this research, a grinder machine with a capacity of 5.5 HP equipped with a 200-micron filter is used. As for the combustion engine, it uses a high-pressure burner with a combustion capability of up to 2000<sup>o</sup> C. To measure the temperature, it uses an Infrared Thermometer with a capacity of up to 1500<sup>o</sup> C. In grouping materials in the form of coarse aggregate and fine aggregate, as well as the process of making and testing concrete samples, several pieces of equipment are used, including a sieve shaker, Digital scales, Slump test, Molen machine, Cylinder tube, Compressive Strength machine,

Figure-1 shows the waste of marble powder before and after experiencing the combustion process.



(a) Marble powder (b) Marble carbon after burning

Figure-1. Marble powder before and after firing.



Figure-2. Process of burning marble waste powder.

Figure-2 below shows the process of burning marble powder waste into graphite carbon. Meanwhile, Figure-3 shows the results of the Scanning Electron Microscope (SEM) laboratory test for marble powder waste

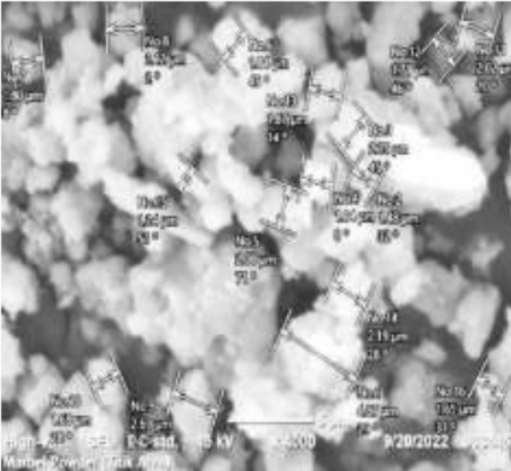


Figure-3. SEM results marble powder.

In testing the compressive strength using the standard Standard Test Method for Compressive Strength of Cylindrical Concrete Specimens ASTM C 39/C 39M - 05 [17].

Table-1. Marble powder elemental compound before Process of burning.

Parameter	Unit	Results
CaO	m/m%	92,820
MgO	m/m%	6,4800
SiO <sub>2</sub>	m/m%	0,5600
Nb <sub>2</sub> O <sub>5</sub>	m/m%	0.0460
MoO <sub>3</sub>	m/m%	0,0344
RuO <sub>4</sub>	m/m%	0,0133
In <sub>2</sub> O <sub>3</sub>	m/m%	0,0114

SnO <sub>2</sub>	m/m%	0,0111
Sb <sub>2</sub> O <sub>3</sub>	m/m%	0,0110
Rh <sub>2</sub> O <sub>3</sub>	m/m%	0,0096

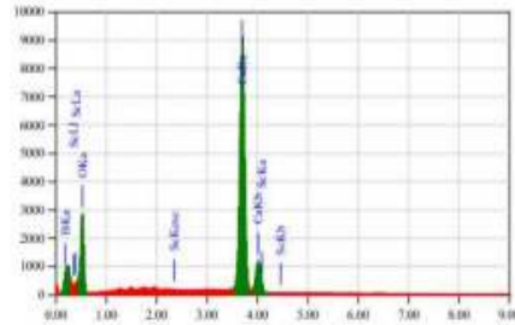


Figure-4. EDS results marble powder.

Table-1 and Figure-4 show the Cao content of marble powder at 92.82%, where this value is a very large percentage in line with the main content in portland cement compounds where the Cao reaches 65, 36 %. [16].

#### Research Procedure

As an initial step in managing raw materials is to carry out the process of refining marble waste. This is intended to accelerate the process of approximation of the particle size similarity with the PCC cement used. Smoothing is done using a grinder machine.

After all the marble waste material is mashed, it is then burnt to obtain carbon particles. Combustion is carried out at temperatures between 850<sup>0</sup> C to 900<sup>0</sup> C for 120 minutes.

After the combustion process is complete, the cooling process is then followed by the cement mixing process through a comparison formulation which includes: 0%, 25%, 30%, 40% and 50%, each of these percentages is the weight of carbon w<sub>31</sub> marble substituted from the weight of cement plan based on the results of the mix design. The design concrete quality target is f<sub>c</sub> 20.75 MPa. Other tests that are also carried out in this phase are structural and chemical laboratory-based tests in the form of concrete microstructure testing using a Scanning Electron microscope (SEM).

The compressive strength test is carried out on a cylindrical sample measuring 15 x 30 cm with an age of 7, 21 and 28 days. The planning stage of the concrete mix (mix design) refers to SNI 7656-2012 [18], regarding the planning process for making normal concrete mixes. The normal concrete is the sample for comparison with the sample object of partial substitution of cement with marble waste.

The number of samples of concrete cylinders made is 240 pieces each are:

- Samples with 0% marble waste = 48 pieces



- Samples with 25% marble waste = 48 pieces
- Samples with 30% marble waste = 48 pieces
- Samples with 40% marble waste = 48 pieces
- Samples with 50% marble waste = 48 pieces

### Curing of Concrete Samples

All concrete samples that have been made are then subjected to a curing process which includes treatment by immersion in fresh water (WCT), immersion in sea water (WCL), natural curing on land / no sea air (DCT) and natural curing on the seashore (DCL) As in Figure-5 below.



(a) Curing at sea/DCL (b) in land/airless areas/DCT



(c) in sea water (WCT) (d) in fresh water (WCT)

Figure-5. Curing process of sample concrete.

24

### Slump Test

To measure the workability of the concrete sample mix, the slump test method is carried out SNI 1972: 2008 [19]. And ASTM C143/C143M-12 [20]. Figure 6 shows the workability measurement process.

Slump or collapse of the concrete mix is the most widely known for monitoring the workability of concrete. The

workability of fresh concrete is related to the  $f_w$  and cement water factor in the micro planes between the cement paste and aggregate during preparation, transportation, and vibration when placing the concrete into the formwork [21].

The compressive strength of concrete is the maximum force per unit area acting on concrete. The compressive strength test of concrete is carried out based on SNI 03-1974-1990 (BSN 1990). The compressive strength of concrete is obtained by the formula:

$$f_c' = P / A \quad (1)$$

Information:

$f_c'$  = compressive strength (MPa)

P = Maximum load force (N)

A = Surface area (mm<sup>2</sup>)



Figure-6. Measurement of workability with a slump test.

Table-2 and Table-3 show the number of samples and marble powder (SSM) for partial replacement of cement into concrete specimens using curing methods which include:

WCT = water curing using fresh water

WCL = water curing using sea water

DCT = curing with land air / non sea air

DCL = dry curing with sea / seaside air

The number of samples for each type of treatment is 48 pieces. In this research, the design quality of concrete compressive strength is K-250 or  $f_c'$  20.75 MPa. Compressive strength testing using a Compressive Strength Digital machine. The number of test object samples consisted of: 48 pcs DCT type, 48 pcs DCL type, 48 pcs WCT type and 48 pcs WCL type, so the total number of samples is 240 pcs.

**Table-2.** Number of samples marble substitution (SSM) for WCT and WCL.

No	CONCRETE SAMPLES	WCT				WCL			
		Sample Age							
		7	14	21	28	7	14	21	28
	SSM-0 % (Normal)	3	3	3	3	3	3	3	3
	SSM - 25 %	3	3	3	3	3	3	3	3
	SSM - 30 %	3	3	3	3	3	3	3	3
	SSM - 40 %	3	3	3	3	3	3	3	3
	SSM - 50 %	3	3	3	3	3	3	3	3

**Table-3.** Number of samples marble powder substitution (SSM) for DCT and DCL.

No	CONCRETE SAMPLES	DCT				DCL			
		Sample Age							
		7	14	21	28	7	14	21	28
	SSM-0 % (Normal)	3	3	3	3	3	3	3	3
	SSM - 25 %	3	3	3	3	3	3	3	3
	SSM - 30 %	3	3	3	3	3	3	3	3
	SSM - 40 %	3	3	3	3	3	3	3	3
	SSM - 50 %	3	3	3	3	3	3	3	3

## RESULTS

### Compressive Strength

Compressive strength testing is carried out on concrete samples that have gone through various concrete curing methods which include: water curing using fresh water (WCT), water curing using sea water (WCL), dry curing with sea / seaside air (DCL) and dry curing with land air / non sea air (DCT). Based on the four sample treatment methods, hereinafter referred to as the WCT type, WCL type, DCL type and DCT type. Each of them carried out a comparison of the quality of its compressive strength carrying capacity. The design concrete quality is K-250 or  $f_c'$  20.75 MPa. The following are the results of each sample test obtained.

Comparison of the compressive strength of DCT type concrete samples against normal concrete (N) with Carbon Graphite marble powder substituted concrete of 25%, 30%, 40% and 50%. From the results of the test analysis, the empirical fact is obtained that all samples of the test object continued to experience an increase in the quality of compressive strength as the sample age increased. The significance of the concrete samples at the age of 28 days from the results of the mix design using the K-250 or  $f_c'$  20.75 MPa quality reference can be shown in Table-3 below. As for each sample of Marble Powder substitution results after being processed into Carbon Graphite Particles can be described as follows:

- Substitution 0 % (normal concrete) = 26.47 MPa > 20.75 MPa

- Substitution 25 % = 22.39 MPa > 20.75 MPa
- Substitution 30 % = 16.56 MPa < 20.75 MPa
- Substitution 40 % = 12.63 MPa < 20.75 MPa
- substitution 50 % = 07.59 MPa < 20.75 MPa

**Table-4.** Comparison of the DCT type pressure test results on all types of Graphite Carbon marble powder substitution.

Concrete Samples	DCT Type			
	7	14	21	28
Substitution 50 %	7.12	7.14	7.20	7.59
Substitution 40 %	7.62	10.70	10.60	12.63
Substitution 30 %	12.21	13.21	14.94	16.56
Substitution 25 %	8.87	17.23	20.90	22.39
Substitution 0 %	17.30	22.73	25.62	26.47

To find out a comparison of the DCT type pressure test results on all types of Graphite Carbon marble powder substitution as shown in Figure 7 below.

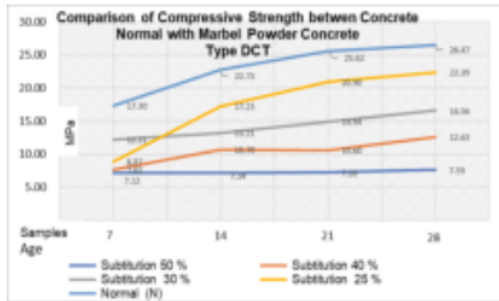


Figure-7. Comparison of the DCT type pressure test results on all types substitution of Graphite Carbon marble powder.

Table-4 and Figure-7 show that normal concrete or concrete without substitute Graphite Carbon Marble Powder, the compressive strength quality is above the planned concrete quality and for the Graphite Carbon Marble Powder concrete quality with a substitution value of 25% cement replacement, it has reached a quality of compressive strength which is also above the design quality, namely  $fc' = 22.39 \text{ MPa} > 20.75 \text{ MPa}$  or 8% above the design concrete quality. As for each of the other substitution compositions it is still below the design concrete quality.

Comparison of the compressive strength of DCL type concrete samples substituted concrete of 25%, 30%, 40% and 50%.

The results of data analysis on the DCL type on concrete samples aged 28 days with comparison of normal concrete quality is  $fc' 20.75 \text{ MPa}$ . This can be shown in Table-4 below. As for each sample of Marble Powder substitution results after being processed into Graphite Carbon Particles can be described as follows:

- Substitution 0 % (normal concrete) = 23,0 MPa > 20,75 MPa
- Substitution 25 % = 22,76 Mpa > 20,75 MPa
- Substitution 30 % = 15,27 Mpa < 20,75 MPa
- Substitution 40 % = 10,70 Mpa < 20,75 MPa
- Substitution 50 % = 07,89 Mpa < 20,75 MPa

Table-5. Comparison of the DCL type pressure test results on all types of Graphite Carbon marble powder substitution.

Concrete Samples	DCL Type			
	7	14	21	28
Substitution 50 %	4.28	5.69	6.68	7.89
Substitution 40 %	7.91	10.11	11.52	10.70
Substitution 30 %	11.65	11.88	15.22	15.27
Substitution 25 %	9.33	17.87	21.41	22.76
Substitution 0 %	17.01	22.08	22.19	23.08

To find out a comparison of the DCL type pressure test results on all types of Graphite Carbon marble powder substitution as shown in Figure-8 below.

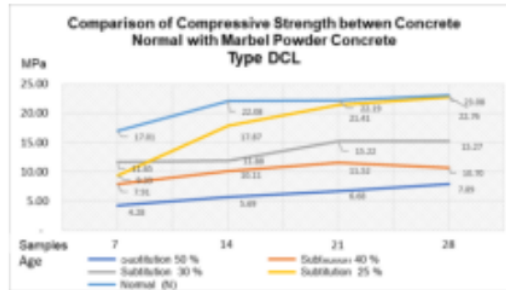


Figure-8. Comparison of the DCL type pressure test results on all types substitution of graphite carbon marble powder.

Figure-8 and Table-5 above show that the DCL type is normal concrete or concrete without substitution (0%) Graphite Carbon Marble Powder, the compressive strength is above the planned concrete quality and for Graphite Carbon Marble Powder concrete quality, the cement substitution value is 25%. Has achieved compressive strength which is also above the design quality, namely  $fc' = 22.76 \text{ MPa} > 20.75 \text{ MPa}$  or 10.1% above the design concrete quality. As for the composition of each of the other substitutions, it is still below the planned concrete quality.

Comparison of the compressive strength of WCT type concrete samples against normal concrete (N) with Graphite Carbon marble powder substituted concrete of 25%, 30%, 40% and 50%.

The results of data analysis on the WCT type on concrete samples aged 28 days with comparison of normal concrete quality is  $fc' 20.75 \text{ MPa}$ . This can be shown in Table-5 below. As for each sample of Marble Powder substitution results after being processed into Graphite Carbon Particles can be described as follows:


- Substitution 0 % (normal concrete) = 21,79 MPa > 20,75 MPa
- Substitution 25 % = 22,14 Mpa > 20,75 MPa
- Substitution 30 % = 14,27 Mpa < 20,75 MPa
- Substitution 40 % = 11,27 Mpa < 20,75 MPa
- Substitution 50 % = 07,69 Mpa < 20,75 MPa



**Table-6.** Comparison of the WCT type pressure test results on all types of Graphite Carbon marble powder substitution.

Concrete Samples	WCT Type			
	Samples Age	7	14	21
Substitution 50 %	6.20	6.70	7.18	7.69
Substitution 40 %	8.05	9.73	8.85	11.27
Substitution 30 %	10.06	13.64	13.26	14.27
Substitution 25 %	9.45	17.31	21.23	22.14
Substitution 0 %	14.66	18.24	20.83	21.79

To find out a comparison of the WCT type pressure test results on all types of Graphite Carbon marble powder substitution as shown in Figure 8 below.

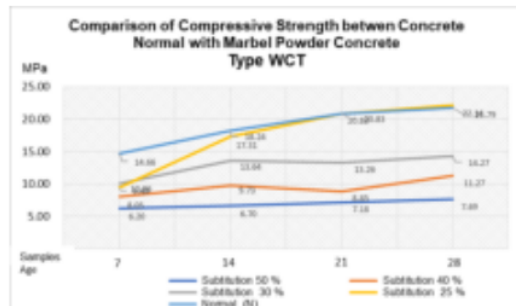

**Figure-9.** Comparison of the WCT type pressure test results on all types substitution of Graphite Carbon marble powder.

Figure-9 and Table-6 above show that the WCT type is normal concrete or concrete without substitutes (0%) Graphite Carbon Marble Powder, the compressive strength is above the quality of the planned concrete and for the quality of Graphite Carbon Marble Powder concrete, the substitution value is 25% cement replacement. Has achieved compressive strength quality which is also above the design quality, namely  $f_c' = 22.14 \text{ MPa} > 20.75 \text{ MPa}$  or is 7% above the design concrete quality. As for each of the other substitution compositions it is still below the design concrete quality.

Comparison of the compressive strength of WCL type concrete samples against normal concrete (N) with Carbon Graphite marble powder substituted concrete of 25%, 30%, 40% and 50%.


The results of data analysis on the WCL type on concrete samples aged 28 days with comparison of normal concrete quality is  $f_c' = 20.75 \text{ MPa}$ . This can be shown in Table-6 below. As for each sample of Marble Powder substitution results after being processed into Graphite Carbon Particles can be described as follows:

- Substitution 0 % (normal concrete) =  $28,00 \text{ MPa} > 20,75 \text{ MPa}$
- Substitution 25 % =  $22,89 \text{ Mpa} > 20,75 \text{ MPa}$
- Substitution 30 % =  $16,69 \text{ Mpa} < 20,75 \text{ MPa}$
- Substitution 40 % =  $12,17 \text{ Mpa} < 20,75 \text{ MPa}$
- Substitution 50 % =  $08,30 \text{ Mpa} < 20,75 \text{ MPa}$

**Table-7.** Comparison of the results of the WCL type pressure test on all types of Carbon Graphite marble powder substitution.

Concrete Samples	WCL Type			
	Samples Age	7	14	21
Substitution 50 %	4.38	6.29	7.66	8.30
Substitution 40 %	7.37	9.89	8.74	12.17
Substitution 30 %	10.76	12.07	15.98	16.69
Substitution 25 %	8.83	16.65	22.02	22.89
Substitution 0 %	20.03	20.28	21.88	23.63

To find out a comparison of the WCL type pressure test results on all types of Graphite Carbon marble powder substitution as shown in Figure-10 below.

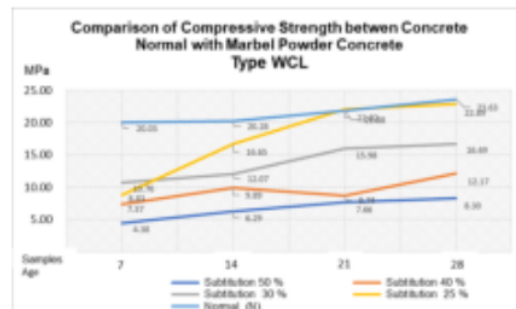

**Figure-10.** Comparison of the WCL type pressure test results on all types substitution of Graphite Carbon marble powder.

Figure-10 and Table-7 above show that the WCL type is normal concrete or concrete without substitution (0%) Graphite Carbon Marble powder, the compressive strength is above the quality of the planned concrete and for the quality of Graphite Carbon Marble Powder concrete, the substitution value is 25% cement replacement. Has achieved compressive strength quality which is also above the design quality, namely  $f_c' = 22.89 \text{ MPa} > 20.75 \text{ MPa}$  or is 10.35% above the design concrete quality. As for each of the other substitution compositions it is still below the design concrete quality.

From the results of the analysis of points 3.1.1 to 3.1.4 on the quality of concrete that meets the requirements for the approach to Mix Design Concrete Quality Plan  $f_c' = 20.75 \text{ MPa}$ , it can be stated as follows:

- For substitution concrete 0 % (normal concrete/ N)





- DCT Type = 26,47 MPa > 20,75 MPa
  - DCL Type = 23,00 MPa > 20,75 MPa
  - WCT Type = 21,79 MPa > 20,75 MPa
  - WCL Type = 28,00 MPa > 20,75 MPa
- b. For substitution concrete 25% Graphite Carbon Particle Marble Powder
- DCT Type = 22,39 Mpa > 20,75 MPa
  - DCL Type = 22,76 Mpa > 20,75 MPa
  - WCT Type = 22,14 Mpa > 20,75 MPa
  - WCL Type = 22,89 Mpa > 20,75 MPa

The results of this study indicate that the use of 25% Graphite Carbon Marble Particle Powder, to replace 25% by volume of cement in making concrete with design quality K-250 or  $f_c'$  20.75 MPa. Obtained concrete quality higher than the concrete quality plan. Figure-11 below shows sample samples for the WCL and DCL types during the pressure test process.



Figure-11. The compressive test process for DCT, DCL, WCT and WCL types of concrete samples.

## CONCLUSIONS

The results of this research indicate that the use of 25% Graphite Carbon Marble Particle Powder, to replace 25% by volume of cement in making concrete with design quality K-250 or  $f_c'$  20.75 MPa. It is obtained that the concrete quality is higher than the planned concrete quality respectively:

- DCT Type = 22,39 Mpa > 20,75 MPa
- DCL Type = 22,76 Mpa > 20,75 MPa
- WCT Type = 22,14 Mpa > 20,75 MPa
- WCL Type = 22,89 Mpa > 20,75 MPa

The compressive strength testing process is carried out based on ASTM C 39/C 39M - 05. Meanwhile, for workability, based on the results of the slump test, a 12 cm slump value is obtained with the testing process referring to SNI 1972: 2008 and ASTM C143/C143M-12. From the conditions mentioned above, it shows that by using Graphite Carbon Particle Marble Powder in reducing the amount of cement in construction work by 25% of the volume of cement planned for concrete in buildings both on the seaside or temperate areas without the influence of sea air including those touching directly with the seawater or fresh water, the concrete quality can still be achieved according to the quality plan. Thus it can be stated that the use of marble waste is a real step in saving the environment

by suppressing the use of cement so that CO<sub>2</sub> emissions from cement factories can also be reduced.

## ACKNOWLEDGEMENT

This research is fully supported by the Ministry of Education and Culture, the Directorate General of Higher Education in the Basic Research Decentralization Program (PDUPT) of Leading Higher Education in Indonesia. [grant number : 0317/E5/AK.04/2022. May 19, 2022] which made this important research feasible and effective.

## REFERENCES

- [1] Muhammad Syarif, Victor S, Wihardi TJ. 2018. Characteristic of compressive and tensile strength using the organic cement compare with portland cement. *Journal Case Studies in Construction Materials*. e00172 (9). Doi.org/10.1016/j.cscm.2018.e00172
- [2] Fran Edwin dan Subar. 2016. Utilization of Marble and Limestone Wastes for Making the Eksposed Bricks Based Synthetic Wollastonite. *Jurnal Teknologi Mineral dan Batubara*. 171-178.
- [3] Dian Rokhmatika Siregar. 2017. Pengaruh Penambahan Limbah Marmer Terhadap Potensial Swelling Pada Tanah Lempung Ekspansif di Daerah Driyorejo. *Jurnal Rekayasa Teknik Sipil*. 3(3): 131-137.
- [4] Selma Kurniawati dan Anastasia Dewi Titisari. 2019. Rekomendasi Pemanfaatan Marmer Berdasarkan Karakteristiknya. *Jurnal Pengabdian kepada Masyarakat*. 5(2): 251-267 DOI:10.22146/jpkm.35963
- [5] Elia Hunggurami, Meriyanti FlowrindaLauata dan Sudiyo Utomo. 2013. Pemanfaatan Limbah Serbuk Batu Marmer Dari Batu Gunung Naitapan Kabupaten Timor Tengah Selatan Pada Campuran Paving blok. *Jurnal Teknik Sipil*. II(1): 37-48.
- [6] Candra Aditya, Dafid Irawan dan Silviana. 2018. Pasir Dari Limbah Marmer Sebagai Bahan Stabilisasi Pada Tanah Ekspansif. *Prosiding Seminar Hasil Penelitian (SNP2M)*: 95-102. ISBN 978-602-60766-4-9. Tahun 2018.
- [7] Susilowati. 2011. Pemanfaatan Serbuk Marmer Sebagai Bahan Pengganti Alternatif Semen Pada Campuran Beton Normal. *Jurnal Arsitektur Universitas Bandar Lampung*. 2(1). juni 2011.
- [8] M. S. Kirgiz. 2016. Advancements in mechanical and physical properties for marble powder-cement



- composites strengthened by nanostructured graphite particles. *Journal Mechanics of Materials* (92): 223-234. Doi.org/10.1016/j.mechmat. 2015.09.013
- [9] Herda Y, Wong Jee Khai, Mehmet Serkan Kirgiz, Moncef L. Nehdi, Omrane Benjeddou, Blessen Skariah Thomas, Styliani Papatzani, Kishor Rambhad, Manoj A. Kumbhalkar, Arash Karimipour. 2022. Transforming Conventional Construction Binders and Grouts into High-Performance Nanocarbon Binders and Grouts for Today's Constructions. *Journal Buildings*. 12(7): 1041. Doi.org/10.3390/buildings12071041
- [10] Arifin Everest, Mulia Pamadi, Andri Irfan Rifai. 2022. Analisa Pengaruh Penambahan Zat Karbon dalam Pembuatan Batako Konvensional. *Journal of Civil Engineering and Planning* ISSN 2746-6299. 3 (1): 75-84.
- [11] Carlos Eduardo Tino Balestra, Lilyanne Rocha Garcez, Leandro Couto da Silva, Márcia Teresinha Veit, Eliziane Jubanski, Alberto Yoshihiro Nakano, Marina, Miguel Angel Ramirez Gil. 2023. Contribution to low-carbon cement studies: Effects of silica fume, fly ash, sugarcane bagasse ash and acai stone ash incorporation in quaternary blended limestone-calcined clay cement concretes. *Journal Environmental Development*. 100792 (45), Doi.org/10.1016/j.envdev.2022.100792
- [12] Elli Mercy Julmile. 2023. Pengaruh Silica Fume dan Pecahan Batu Marmer Sebagai Bahan Substitusi Pada Campuran Beton. *Jurnal Civil Engineering Journal*. 5(1). DOI: <https://doi.org/10.52722/pcej.v5i1.588>
- [13] Bing Liu Songyuan Geng, Junpeng Ye, Xiaoyan Liu, Weixin Lin, Shihao Wu, Kai Qian. 2023. A preliminary study on waste marble powder-based alkali-activated binders. *Journal Construction and Building Materials* (378). Doi.org/10.1016/j.conbuildmat.2023.131094.
- [14] Kechkar Chiraz, Kherraf Leila, Houria Hebhoub, Assia Abdelouahid. 2022. The Comparative Study Of The Performance Of Concrete Made From Recycled Sand" *The Civil Engineering Journal*. 31(3): 415-426. DOI 10.14311/CEJ.2022.03. 0031.
- [15] Elyas Asadi Shamsabadi, Naeim Roshan, S. Ali Hadigheh, Moncef L. Nehdi, Ali Khodabakhshian, Mansour Ghaleh novi. 2022. Machine learning-based compressive strength modelling of concrete incorporating waste marble powder. *Journal Construction and Building Materials*. 126592 (324). Doi.org/10.1016/j.conbuildmat. 2022.126592
- [16] Muhammad Syarif, Victor Sampebulu, M. Wihardi Tjaronge, Nasruddin. 2018. Characteristic of compressive and tensile strength using the organic cement compare with portland cement. *Case Studies in Construction Materials*. Volume 9, December 2018, e00172. Doi.org/10.1016/j.cscm.2018.e00172
- [17] America Society for Testing and Material, (ASTM). Designation C 39/C 39M - 05. Standard Test Method for Compressive Strength of Cylindrical Concrete Specimens. Edition Approved, October 2008.. Published July 2008. Annual book Of ASTM Standards. 14(01).
- [18] SNI 7656: 2012. Tata cara pemilihan campuran untuk beton normal, beton berat dan beton massa.
- [19] SNI 1972: 2008. Cara Uji Slump Beton. Badan Standarisasi Nasional. ICS 91.100.30.
- [20] American Society for Testing and Material, (ASTM). Designation C 143/C 143M - 03. Standard Test Method for Slump of Hydraulic-Cement Concrete. Annual Book of ASTM Standards, Vol. 04.02. Current edition approved July 10, 2003. Published September 2003.
- [21] Muhammad Syarif, Mehmet Serkan Kirgiz, André Gustavo de Sousa Galdino, M. Hesham El Naggar, Jahangir Mirza, Jamal Khatib, Said Kenai, Moncef Nehdi, John Kinuthia, Anwar Khitab, Carlos Thomas, Ravindran Gobinath, Muhammad Irfan Ul Hassan, Yan Kai Wu, Ahmed Ashteyat, Ahmed Soliman, Khairunisa Muthusamy, Thaarrini Janardhanan, Trinity Ama Tagbor, Tuan Anh Nguyen Chandra Sekhar Tiwary. 2021. Development and assessment of cement and concrete made of the burning of quarry by product. *Journal of Materials Research and Technology*. (15): 3708-3721. Doi.org/10.1016/j.jmrt. 2021.09.140.

# REDUCING THE USE OF CEMENT WITH MARBLE WASTE FOR

## ORIGINALITY REPORT

20%

SIMILARITY INDEX

16%

INTERNET SOURCES

12%

PUBLICATIONS

6%

STUDENT PAPERS

## PRIMARY SOURCES

1	Submitted to California State University, Fresno Student Paper	3%
2	garuda.kemdikbud.go.id Internet Source	2%
3	www.mdpi.com Internet Source	1%
4	Submitted to Universiti Teknologi Malaysia Student Paper	1%
5	profdoc.um.ac.ir Internet Source	1%
6	profesis.ckait.cz Internet Source	1%
7	repositorio.unesp.br Internet Source	1%
8	doi.org Internet Source	1%
9	Mehmet Serkan Kirgiz. "Advancements in mechanical and physical properties for	1%

marble powder-cement composites  
strengthened by nanostructured graphite  
particles", Mechanics of Materials, 2016

Publication

---

10	<a href="http://media.neliti.com">media.neliti.com</a> Internet Source	1 %
11	<a href="http://digilib.unismuh.ac.id">digilib.unismuh.ac.id</a> Internet Source	1 %
12	<a href="http://jurnal.poliupg.ac.id">jurnal.poliupg.ac.id</a> Internet Source	1 %
13	<a href="http://garuda.ristekdikti.go.id">garuda.ristekdikti.go.id</a> Internet Source	1 %
14	<a href="http://www.its.ac.id">www.its.ac.id</a> Internet Source	<1 %
15	Bing Liu, Songyuan Geng, Junpeng Ye, Xiaoyan Liu, Weixin Lin, Shihao Wu, Kai Qian. "A preliminary study on waste marble powder-based alkali-activated binders", Construction and Building Materials, 2023 Publication	<1 %
16	<a href="http://dgescholar.acemap.info">dgescholar.acemap.info</a> Internet Source	<1 %
17	<a href="http://ir.canterbury.ac.nz">ir.canterbury.ac.nz</a> Internet Source	<1 %
18	Oktavia Kurnianingsih, Muhammad Abid, Haidar Putra Firdaus, Hasan Tri Ashari.	<1 %

"Waste and Marble Waste Variations on the Compressive Strength and Permeability of Porous Concrete", IOP Conference Series: Earth and Environmental Science, 2024

Publication

19

Tao Wang, Long Chen, Fen Wen, Kaizhong Ding, Shuangsong Du, Chunlong Zou.

"Conceptual Design of 3-T All HTS MRI using No-Insulation Winding Technology: Electromagnetic Stress Reinforcement Structure", 2020 IEEE International Conference on Applied Superconductivity and Electromagnetic Devices (ASEMD), 2020

Publication

<1 %

20

[inotera.poltas.ac.id](http://inotera.poltas.ac.id)

Internet Source

<1 %

21

Yasin Onuralp Özkılıç, Özer Zeybek, Alireza Bahrami, Ali İhsan Çelik et al. "Optimum Usage of Waste Marble Powder to Reduce Use of Cement toward Eco-friendly Concrete", Journal of Materials Research and Technology, 2023

Publication

<1 %

22

Submitted to Middle East College of Information Technology

Student Paper

<1 %

23

Submitted to Silpakorn University

Student Paper

<1 %

24	<a href="https://hdl.handle.net">hdl.handle.net</a> Internet Source	<1 %
25	<a href="https://accentsjournals.org">accentsjournals.org</a> Internet Source	<1 %
26	Andi Haslindah, Ilham Idrus, Try Agung Basuki, Sultan Saiful. "Proses Pengelolaan Limbah Marmer Menjadi Produk Paving Block", Journal Industrial Engineering & Management (JUST-ME), 2020 Publication	<1 %
27	<a href="https://link.springer.com">link.springer.com</a> Internet Source	<1 %
28	Alfan Safari, Agustinus Agus Setiawan. "Pemanfaatan Limbah Batu Marmer sebagai Substitusi Parsial Agregat Kasar pada Campuran Beton terhadap Kuat Tekan Beton", Dinamika Rekayasa, 2023 Publication	<1 %
29	Aurelius Dario, Riza Suwondo. "The influence of crystalline technology as concrete admixture on compressive strength and permeability", IOP Conference Series: Earth and Environmental Science, 2024 Publication	<1 %
30	E K Pangestuti, S Handayani, H Adila, P Primerio. "The effect of polypropylene fiber addition to mechanical properties of	<1 %

concrete", IOP Conference Series: Earth and Environmental Science, 2021

Publication

31

Yoke Lestyowati, Henny Herawati, Budi Satria Panandita. "EXPERIMENTAL FLEXURAL STRENGTH OF GLASS FIBER REINFORCED POLYMER (GFRP) HYBRID REINFORCED CONCRETE BEAMS", Jurnal Teknik Sipil, 2023

Publication

<1 %

32

[discovery.ucl.ac.uk](https://discovery.ucl.ac.uk)

Internet Source

<1 %

33

[ia802802.us.archive.org](https://ia802802.us.archive.org)

Internet Source

<1 %

34

[www.etasr.com](http://www.etasr.com)

Internet Source

<1 %

35

Zulmahdi Darwis, Woelandari Fathonah, Lukmanul Hakim. "Utilization of Steel Slag Waste as a Substitute for Coarse Aggregate in Concrete Mixture", Materials Science Forum, 2023

Publication

<1 %

36

"Research into action", Building Research & Information, 1991

Publication

<1 %

37

Carlos Eduardo Tino Balestra, Lilyanne Rocha Garcez, Leandro Couto da Silva, Márcia Teresinha Veit et al. "Contribution to low-

<1 %

carbon cement studies: Effects of silica fume, fly ash, sugarcane bagasse ash and acai stone ash incorporation in quaternary blended limestone-calcined clay cement concretes", Environmental Development, 2022

Publication

---

Exclude quotes      On

Exclude matches      Off

Exclude bibliography      On